

# Feasibility Study of Affordable Earth Masonry Housing in the U.S. Gulf Coast Region

Nitin Kumar, S.M.ASCE<sup>1</sup>; Michele Barbato, M.ASCE<sup>2</sup>; and Robert Holton<sup>3</sup>

**Abstract:** Compressed and stabilized earth block (CSEB) structural systems represent a sustainable low-cost alternative to other construction systems that are common in industrialized countries. The wide availability of suitable soils makes these structural systems attractive for building affordable housing worldwide. Currently, CSEB construction in the USA is mainly used in dry and arid regions and has rarely been used in humid climates. In this work, a structural, architectural, and economic feasibility study for CSEB structural systems in the U.S. Gulf Coast region is presented. The structural feasibility study presented in this paper included the identification of locally available soils for CSEB fabrication; experimental investigation of mechanical properties of CSEB and mortar as function of their composition; durability study for a CSEB wall with and without protective plastering; and calculation of wind resistance for a representative CSEB house. The architectural feasibility study investigated the use of CSEB systems in vernacular housing typologies of Southern Louisiana. Finally, the economic feasibility study compared the cost of a reference house built using CSEBs and other more common construction materials. The results obtained in this study suggest that CSEB systems have the potential to provide a modern, cost-effective, sustainable, hurricane-resistant housing construction system as an alternative to more common constructions systems in the U.S. Gulf Coast region. DOI: [10.1061/\(ASCE\)AE.1943-5568.0000311](https://doi.org/10.1061/(ASCE)AE.1943-5568.0000311). © 2018 American Society of Civil Engineers.

**Author keywords:** Earth block construction; Feasibility study; Affordable housing; Hurricane-resistant housing.

## Introduction

A significant portion of the world's population currently lives in earth-based dwellings (Avrami et al. 2008). Earth construction provides several advantages over other traditional construction methods (e.g., reinforced concrete, fired masonry, and wood construction). In particular, earth construction is: (1) affordable and locally appropriate, since inexpensive and locally available soils are used as the primary structural materials (Morton et al. 2005; Minke 2012); (2) energy and humidity efficient, due to its relatively high volumetric heat capacity and excellent ability to passively maintain a healthy indoor relative humidity (Pacheco-Torgal and Jalali 2011; Minke 2012); and (3) environmentally friendly, with an embodied energy that can be over 80% lower than that of concrete masonry units and fired clay bricks (Morton et al. 2005; Pacheco-Torgal and Jalali 2011).

Earth construction is also one of the most ancient and sustainable approaches for building construction, dating back over 9000 years (Minke 2012), and with examples found all over the world (Gandreau and Delboy 2012). Different earth construction techniques were developed over the centuries, the most prominent of which are cob construction, rammed earth construction, and earth block or adobe construction (Weismann and Bryce 2006; Pacheco-Torgal and

Jalali 2011). These traditionally built earth structures (i.e., nonengineered constructions) are not capable of resisting extreme loads from natural hazards such as earthquakes and strong winds, due to the inherent brittleness of the material (Klingner 2006; Blondet et al. 2008; Korkmaz et al. 2010; Gomes et al. 2011; Sayin et al. 2013); therefore, they are inadequate for mainstream modern construction. However, in the last few decades, significant research has been devoted to develop engineered earth blocks as a more affordable and ecologically friendly alternative to other masonry elements, e.g., fired bricks and concrete blocks (Inter-American Housing Planning Center 1964; Webb 1988; Gooding 1994; Houben and Guillaud 1994). Consequently, engineered earth block construction has emerged as a viable modern construction technique, due to its eco-efficiency and extreme affordability (Deboucha and Hashim 2011; Pacheco-Torgal and Jalali 2011). In particular, earth block construction is a promising technique because (1) its individual components (i.e., earth block and mortar) can be engineered to improve their strength and durability (Houben and Guillaud 1994; Rigassi 1995; Kerali 2001), and (2) the construction technique has many commonalities with ordinary masonry (Rigassi 1995), for which extensive experience and a vast engineering literature are available. Modern earth blocks can be categorized into three different broad categories: (1) compressed earth blocks (CEBs), which are produced by compressing an appropriate soil mix with the help of a hydraulic or a manual press (Delgado and Guerrero 2007; Pacheco-Torgal and Jalali 2011; Brown et al. 2014); (2) stabilized earth blocks (SEBs), which are made from a soil mix that is stabilized using a chemical binder such as Portland cement or lime (Guettala et al. 2002); and (3) compressed and stabilized earth blocks (CSEBs), which are fabricated by mechanically compressing a stabilized soil mix (Kerali 2001; Riza et al. 2011). CSEBs use both mechanisms of CEBs and SEBs to form strong and durable earth blocks, which are more suitable than other earth blocks to satisfy modern construction requirements.

Currently, earth construction in the USA is mainly used in dry and arid regions, e.g., New Mexico, Colorado, Arizona, California,

<sup>1</sup>Ph.D. Student, Dept. of Civil and Environmental Engineering, LA State Univ., Baton Rouge, LA 70803. E-mail: nkuma12@lsu.edu.

<sup>2</sup>Associate Professor, Dept. of Civil and Environmental Engineering, LA State Univ., 3230B Patrick F. Taylor Hall, Baton Rouge, LA 70803 (corresponding author). ORCID: <https://orcid.org/0000-0003-0484-8191>. E-mail: mbarbato@lsu.edu

<sup>3</sup>Assistant Professor, School of Architecture, LA State Univ., Baton Rouge, LA 70803. E-mail: rholton@lsu.edu.

Note. This manuscript was submitted on July 17, 2017; approved on December 8, 2017; published online on April 10, 2018. Discussion period open until September 10, 2018; separate discussions must be submitted for individual papers. This paper is part of the *Journal of Architectural Engineering*, © ASCE, ISSN 1076-0431.

and West Texas (Windstorm and Schmidt 2013). New Mexico has also incorporated the use of earth blocks for non-hurricane-prone areas into the state's building code (NMAC 2009). However, CSEB construction has rarely been used in the U.S. Gulf Coast region (Hall et al. 2012) because of the poor resistance to degradation generally experienced by earth construction in a humid and rainy climate (Kerali 2001), and the widespread perception of earth construction as a standard choice for resistance to extreme wind loads. By contrast, recent research based on structural analysis results and controlled laboratory experiments has demonstrated that earth masonry can safely withstand extreme wind loads (Matta et al. 2015) and impacts of windborne debris (Geiger 2011, Cuéllar-Azcárate and Matta 2016) due to hurricanes or tornadoes.

This study investigated the feasibility of CSEB systems as a hurricane-resistant, affordable, and durable housing typology that can be reliably used even in the U.S. Gulf Coast's humid climate. This study includes the investigation of structural, architectural, and economic feasibility of a typical earth block house compared with one of a similar size built with common construction techniques. A preliminary investigation of the use of a soil-cement plaster protection for CSEB walls is also presented as part of the structural feasibility study.

## Motivation and Significance

A significant portion of the U.S. population (including a significant number of underrepresented and underprivileged groups) live in rural and remote areas, particularly in Louisiana. In these rural areas, affordable housing is key to reducing homelessness, creating jobs, and fostering economic development. According to data published by the U.S. Department of Housing and Urban Development in 2010, 386,000 low-income households in Louisiana are in need of affordable housing (LHFA 2010). The National Association of Home Builders (Emrath 2014) estimates that, for each newly built house, three full-time equivalent new jobs are created, particularly in the construction and manufacturing industry, and \$111,000 in government revenue (including income taxes, government social insurance, permit and license fees, and sales taxes) is generated (\$74,400 in federal taxes and \$36,600 in state and local taxes). This estimate does not include the indirect economic impact of the new house, e.g., due to the relocation and future earnings of the building owners, which is generated over a prolonged period of time. The critical demand for low-cost housing in the U.S. Gulf Coast region is exacerbated by recurring tropical storms, flooding events, subsidence, and rising water levels, as recently documented by Davenport and Robertson (2016), in which thousands of residents across southern Louisiana were displaced by the land loss induced by coastal erosion and climate change effects.



In our current period of rising global temperatures, unpredictable events have displaced and will continue to displace thousands of residents in the coastal region of Louisiana. This historic unseating of entire communities necessitates a reconsideration of standard housing solutions. Constructed primarily of materials accessible from the building site, CSEB design and building techniques offer an economical and sustainable approach to the current increase in demand for affordable weather resistant housing. The research presented in this paper proposes the novel use of CSEBs in a hot wet environment and provides the preliminary engineering basis needed to offer affordable, resilient, and sustainable housing for the many individuals in need in the U.S. Gulf Coast region.

## Structural Feasibility Study

The structural feasibility of CSEB housing in the U.S. Gulf Coast region depends on the mechanical properties of CSEB elements (i.e., blocks and mortar) and CSEB systems (e.g., walls and pillars). These properties need to satisfy several minimum standard requirements to ensure sufficient resistance of the construction to extreme winds as those associated with hurricanes. In addition, the CSEB walls need to achieve a sufficient durability when exposed to the humid weather typical of this region of the U.S. The CSEB mechanical properties depend mainly on the properties and composition of the available soil, the fabrication process, and the amount of stabilizer used in the soil mix. This section presents: (1) the identification of appropriate soil in the East Baton Rouge area, (2) the description of the CSEB fabrication process adopted in this study, (3) the investigation of the mechanical properties of CSEBs as a function of the amount of cement used as stabilizer, (4) the investigation of the mechanical properties of soil-based mortar as a function of cement and sand content, (5) a durability study of an actual CSEB wall subject to the humid weather in Baton Rouge, and (6) the estimation of the resistance of the main wind-force resisting system for a hypothetical house built using locally produced CSEBs. It is noted here that Portland cement was used as the stabilizer material and as an ingredient of the weather protection plaster. This preliminary selection was made based on the wide availability of this material and on existing literature, which suggests that cement is highly efficient in increasing the mechanical strength and durability of CSEBs (Kerali 2001; Guettala et al. 2006). However, other more sustainable solutions could also be considered in future studies, e.g., using lime as stabilizer (Hall et al. 2012) or modifying foundations, roofing, and building geometry to minimize weather effects in rainy environments (Guillaud et al. 1995), and/or investigating other rendering solutions to protect building envelopes [e.g., earthen plasters stabilized with lime, acrylic emulsions, polymers, asphalt emulsions, agave juice, see Taylor (1988, 1990)].

## Soil Identification

Production of high-quality CSEBs requires soils with specific compositions, i.e., the appropriate proportions of sand, silt, and clay contents. The existing literature provides recommended soil composition ranges for fabrication of CEBs (Gooding 1994; Rigassi 1995; Delgado and Guerrero 2007; Pacheco-Torgal and Jalali 2011). These soil compositions can be obtained through a particle size analysis and can be classified using the Unified Soil Classification System (USCS) (ASTM 2010a). Fig. 1(a) shows the United State Department of Agriculture (USDA 1999) soil texture triangle, which provides a graphical representation of the composition of a soil. In this figure, the thick blue line identifies the optimal soil compositions for fabricating CEBs, the thick magenta dashed line identifies suboptimal soil compositions that can still be used for CEBs, and the region outside the above lines represents soil compositions that are generally considered inappropriate for CEB fabrication, according to the existing literature. Additional criteria were suggested in terms of Atterberg limits (ASTM 2010b), e.g., with optimal liquid limits (LL) ranging from 25 to 50, and optimal plasticity indexes (PI) ranging from 2.5 to 29 (Delgado and Guerrero 2007; Pacheco-Torgal and Jalali 2011). It is noted here that only scarce information is available in the literature for optimal soil compositions and Atterberg limits for fabrication of CSEBs. However, it is reasonable to expect that a wider range of soil compositions and values of Atterberg limits would be considered acceptable when compared to those for CEB fabrication, since the soil can be partially ameliorated by using appropriate stabilizers.

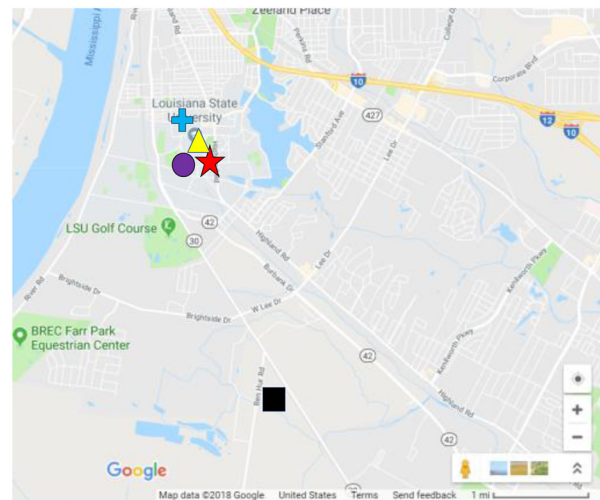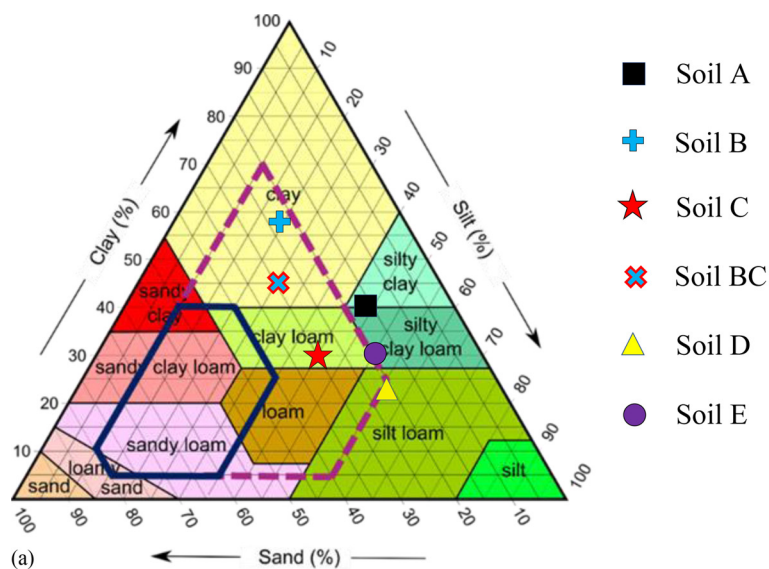

**Fig. 1.** Tested soils: (a) USDA soil texture triangle with optimal soil grading region and composition of tested soils from Baton Rouge, LA and (b) map of Baton Rouge with site locations of different soils (map data © 2018 Google)

Soil samples were taken from five different locations (A, B, C, D, and E) in Baton Rouge from the layer between 1 m (3.28 ft) and 2 m (6.56 ft) below the surface, as shown in Fig. 1(b). Simple preliminary in situ tests (i.e., “cigar” and jar tests) were used to determine whether these soils were appropriate for CSEB fabrication based on suggestions provided in the literature (Rigassi 1995). The average “cigar” lengths were in the range of 12–15 cm [see Fig. 2(a)], which is considered an acceptable range for CEB fabrication (Rigassi 1995). In the jar test, only one layer of soil particle was observed for all soils, as shown in Fig. 2(b), which indicates that these soils contained almost exclusively fine particles (i.e., silt and clay).

After performing in-situ tests, the granulometry and Atterberg limits of the soil samples were obtained by performing standard laboratory tests. The results of the particle size analysis, performed according to ASTM D6913-04 (ASTM 2009) and ASTM D7928-16 (ASTM 2016b), are presented in Fig. 3 and were used to classify the different soils on the USDA soil texture triangle presented in Fig. 1(a). The Atterberg limits were measured according to ASTM D4318-10 (ASTM 2010b). The LL were 35.5%, 30%, 28%, 27.5%, and 26.5% for soils A, B, C, D, and E, respectively; whereas the PI were 12.5%, 8.0%, 11.5%, and 12% for soils A, B, C, D, and E, respectively. The results of the laboratory test indicate that the used soils (1) had LL and PI values within the optimal ranges, and (2) lay within the suboptimal composition region (soils B and C) or immediately outside this region as identified on the USDA soil texture triangle (see Fig. 1). The soils used in this study are representative of the soil available in the East Baton Rouge area.

### Fabrication Process of CSEBs

The fabrication of CSEBs, and in particular the compaction process, can significantly affect the mechanical and physical properties of CSEBs (Lunt 1980; Gooding 1994). CSEBs can be fabricated using: (1) quasi-static compaction, through a slowly applied pressure in single-side compaction, double-side compaction, or extrusion (Gooding 1994; Maillard and Aubert 2014); or (2) dynamic compaction, through impact or vibration (Meriani 2008). Quasi-static compaction is most commonly applied by using manually-operated or hydraulic compression machines. A single-stroke

manual one-side compaction machine made of steel was fabricated specifically for this study and is shown in Fig. 4.

CSEB fabrication was performed by: (1) extracting, drying, and pulverizing the soil; (2) sieving the pulverized soil to remove any organic and coarse particles; (3) weighing the soil, cement, and water to obtain the desired amounts; (4) mixing soil and cement thoroughly with the help of a power-driven mixer for at least 10 min; (5) adding water to the soil-cement blend in multiple steps while mixing it; and (6) compressing the wet soil-cement blend by using the compaction machine to form blocks. The production time between material mixing and the fabrication of all blocks was maintained below 45 minutes for all batches, to avoid excessive curing of the cement. Each batch consisted of five to eight blocks. After fabrication, the blocks were cured for 28 days by wet-and-dry curing (Rigassi 1995), i.e., the blocks were wrapped in a plastic sheet inside the laboratory for the first 14 days to maintain a high humidity environment and avoid rapid evaporation and formation of shrinkage cracks, then they were left to dry for 14 additional days without being directly exposed to sun and wind.

### Mechanical Properties of CSEBs

This study investigated the effects of different amounts of cement used as a stabilizer on the compressive and flexural strength of earth blocks made with soil from East Baton Rouge, LA. Compressed earth blocks of 290 mm × 150 mm × 75 mm (11.41 in × 5.90 in × 2.95 in) were fabricated with soil A and different percentages in weight (wt%) of Type II Portland cement (PC), namely 0 wt% (CEB), 3 wt% (CSEB03), 6 wt% (CSEB06), 9 wt% (CSEB09), and 12 wt% (CSEB12). Five equally-built specimens for each cement content of CSEBs were tested using an MTS universal testing machine with a 50 kN load cell capacity to determine the block’s average dry compressive strength,  $f_{bd}$ , wet compressive strength,  $f_{bw}$ , and modulus of rupture (MOR). The specimens were loaded in displacement-control mode at a rate of 2 mm/min.

First, a three-point bending flexure test was performed on the full-size blocks (NMAC 2009). The displacement was applied at the middle of the block with a 20-mm distance between edge and support, giving a 250-mm clear span, as shown in Fig. 5(a). Fig. 6 plots the applied load–midspan deflection curves for all tested

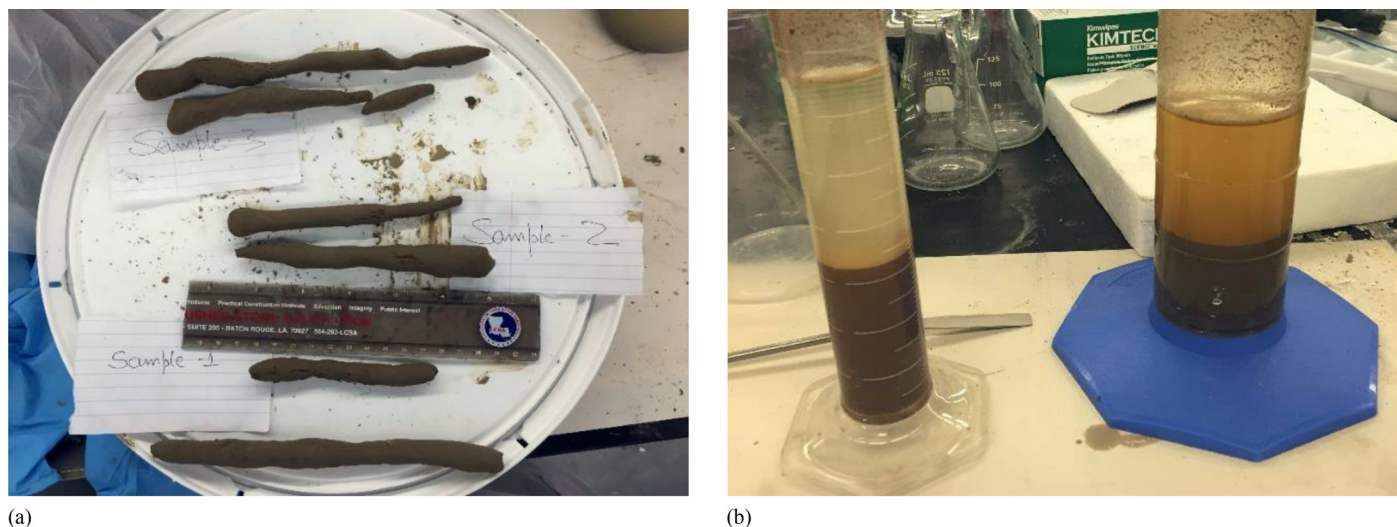


Fig. 2. In situ soil identification tests: (a) cigar test and (b) jar test

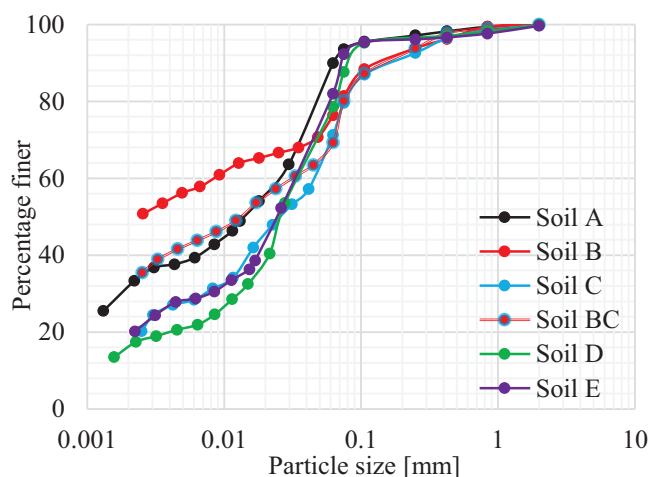


Fig. 3. Grain size analysis of soils collected from different locations in Baton Rouge, LA

specimens. The results of the flexure test in terms of sample means, minimum/maximum values, and coefficients of variation for MOR and modulus of elasticity (MOE) are reported in Table 1. The flexure test resulted in the formation of a well-defined large crack in the middle of the earth blocks. The two halves of each tested specimen, produced by the fracture of the block in the flexure test, were trimmed using masonry cutting tools to produce two specimens of 100 mm  $\times$  100 mm  $\times$  75 mm (3.93 in  $\times$  3.93 in  $\times$  2.95 in) to be used in a direct compression test (Walker 1996). For each cement content, five half-block specimens (one from each original earth block) were tested for dry compression tests, whereas the remaining five specimens were immersed in water for 24 h before being tested for wet compressive strength. Neoprene pads were placed between the steel plates and test specimens during each compression test.

Figs. 7(a and b) plot the stress-strain curves for all tested specimens corresponding to the dry and wet compression tests, respectively. The results of the dry and wet compression tests in terms of sample means, minimum/maximum values, and coefficients of variation for compressive strength and MOE are reported in Table 1, which also reports the estimate of the characteristic uniaxial dry and wet compressive strengths,  $f_{bkd}$  and  $f_{bkw}$  respectively,

accounting for shape and aspect ratio corrections (Middleton and Schneider 1992). The failure mode observed during wet and dry compression tests corresponded to the development of an hour-glass shape following the spalling of the vertical sides of the tested specimen, as shown in Fig. 5(b). This failure mode is similar to that commonly observed in compression tests of typical concrete cubic specimens.

The average MOR of the CSEBs was 18% to 136% higher than the average MOR of CEBs due to an increase in cement content from 3 wt% to 12 wt%. The average dry compressive strength of CSEBs was 36% to 219% higher than the average dry compressive strength of CEBs due to an increase in cement content from 3 wt% to 12 wt%. For the wet compressive strength, CEBs showed a strength equal to zero, since the blocks dissolved after 24 h of water submersion. The average wet compressive strength of CSEBs increased by 29%, 111%, and 188% for the CSEB06, CSEB09, and CSEB12, respectively, when compared to the strength of the CSEB03. The wet compressive strength is significantly lower than the dry compressive strength for equal amounts of cement content. In particular, the average wet compressive strengths of CSEB03, CSEB06, CSEB09, and CSEB12 are 55%, 52%, 47%, and 44% lower than the corresponding dry compressive strength. This reduction in the compressive strength can be attributed to the development of pore water pressures and a decrease in soil cohesion. As expected, for all three sets of tests, the strength of the CSEBs increased with increasing cement content. In addition, it was observed that the MOE measured in all tests also followed the same trend as the corresponding strength, i.e., it increased with increasing cement content.

These experimental results were compared to the minimum requirements suggested in current design codes and existing literature. In particular, the New Mexico Administrative Code (NMAC 2009) recommends a minimum average dry compressive strength of 2.07 MPa (300 psi), a minimum sample dry compression strength of 1.72 MPa (250 psi), and a minimum average MOR of 0.35 MPa (50 psi) for compressed earth blocks. In addition, in humid environments, CSEBs should also have a minimum average wet compressive strength of 1.5 MPa (Lunt 1980; Houben and Guillaud 1994) or a minimum unconfined characteristic wet compressive strength of 1.0 MPa (Walker and Stace 1997). From the results obtained in this study, it is observed that CSEB09 and CSEB12 satisfied these strength requirements.

## Mechanical Properties of Soil-Based Mortar

The mechanical properties of cement-soil mortars produced with the same soil used for CSEBs were investigated to identify mortars that are compatible with the earth blocks for the construction of CSEB structures. It is noteworthy that the New Mexico Administrative Code allows the use of both soil-cement mortar and conventional mortars for CSEB walls (NMAC 2009); however, Venkatarama Reddy and Gupta (2005; 2006) suggested that soil-cement mortars can provide better bond strength, higher initial stiffness, and lower cost than conventional cement-based mortar.

In particular, the effects on the compressive strength of soil-based mortar were investigated for: (1) different amounts of cement used as a stabilizer (soil-cement mortar) and (2) different amounts of sand used to ameliorate the soil for a fixed 15 wt% cement content (soil-sand-cement mortar). Mortar cubes with a side dimension equal to 50 mm were fabricated by adding: (1) different amounts of Type II PC (varying between 3 wt% and 30 wt%, with increment intervals of 3 wt%) to soil A and (2) different amounts of sand (varying between 10 wt% and 50 wt%, with increment intervals of

10 wt%) to a mix of soil A and 15 wt% cement. The samples were tested after being cured for 28 days (using the same curing procedure used for the CSEBs) to obtain the average dry compressive strength of the mortar,  $f_m$  (ASTM. 2016a). The results of the compression tests in terms of sample means and coefficients of variation for the dry compressive strength and MOE as functions of the cement and sand contents are reported in Table 2 together with the estimates of the unconfined characteristic compressive strength of the mortar,  $f_{mk}$  (SNZ 1998).

The results indicate that the soil-cement mortar compressive strength increases with increasing cement content. However, a significantly larger cement content is required to achieve a compressive strength that is comparable to that of the CSEBs. In particular, a soil-cement mortar with at least 24 wt% and 30 wt% cement contents should be used with CSEB09 and CSEB12 blocks, respectively. This result is most likely due to the high clay content (35–40 wt%) in the soil, which is significantly higher than the amount recommended for soil-cement mortar in CSEB masonry, i.e., up to 10–20 wt% of clay (Walker 1999; Venkatarama Reddy and Gupta 2005, 2006).

As expected, the addition of sand was found to increase the mortar compressive strength for a given amount of cement. It was



Fig. 4. Single-stroke manually-operated one-side compaction machine

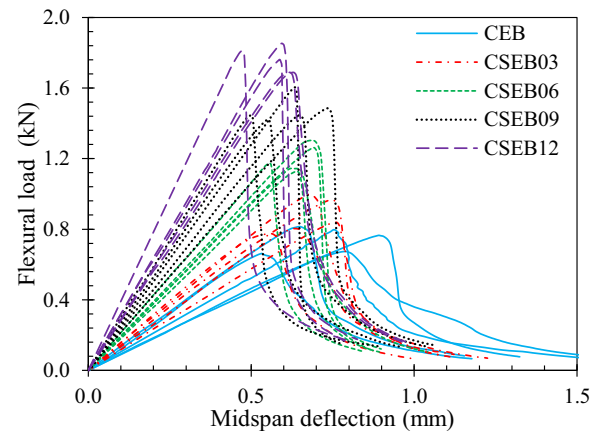


Fig. 6. Load-displacement curves from flexure test of CSEBs



(a)



(b)


Fig. 5. Experimental mechanical tests: (a) specimen after flexure test and (b) specimen after compression test

**Table 1.** Mechanical Properties of CSEBs for Different Cement Contents

Test	Cement content (%)	Strength*				MOE				$f_{bk}^{**}$ (MPa)
		Min. (MPa)	Max. (MPa)	Avg. (MPa)	COV (%)	Min. (MPa)	Max. (MPa)	Avg. (MPa)	COV (%)	
Flexure	0	0.29	0.36	0.33	9.50	56.40	82.86	67.00	17.10	—
	3	0.34	0.44	0.39	11.40	71.18	97.63	86.26	12.36	—
	6	0.50	0.58	0.53	6.38	109.90	130.29	118.84	6.38	—
	9	0.63	0.71	0.66	4.87	131.33	180.78	154.47	12.49	—
	12	0.75	0.82	0.78	4.17	170.49	241.86	194.90	14.39	—
Dry compression	0	1.15	1.33	1.22	6.38	19.42	25.93	23.28	11.40	0.74
	3	1.51	1.86	1.66	8.74	29.90	50.20	38.53	20.49	0.96
	6	1.83	2.16	2.01	6.13	36.95	51.33	44.82	11.47	1.23
	9	2.70	3.27	2.97	7.19	59.05	62.27	60.45	2.34	1.78
	12	3.73	4.24	3.89	5.47	62.28	88.96	74.20	13.41	2.42
Wet compression	0	—	—	—	—	—	—	—	—	—
	3	0.72	0.81	0.75	4.91	17.26	25.48	22.07	14.53	0.47
	6	0.88	1.11	0.97	9.91	22.17	27.76	24.33	8.97	0.54
	9	1.51	1.68	1.58	4.32	37.03	54.05	44.63	15.46	1.01
	12	1.98	2.33	2.16	5.84	48.00	58.19	52.21	7.26	1.34

\*Strength = MOR for flexure test,  $f_{bd}$  for dry compression test, and  $f_{bw}$  for wet compression test.

\*\* $f_{bk} = f_{bkd}$  for dry compression test, and  $f_{bkw}$  for wet compression test.

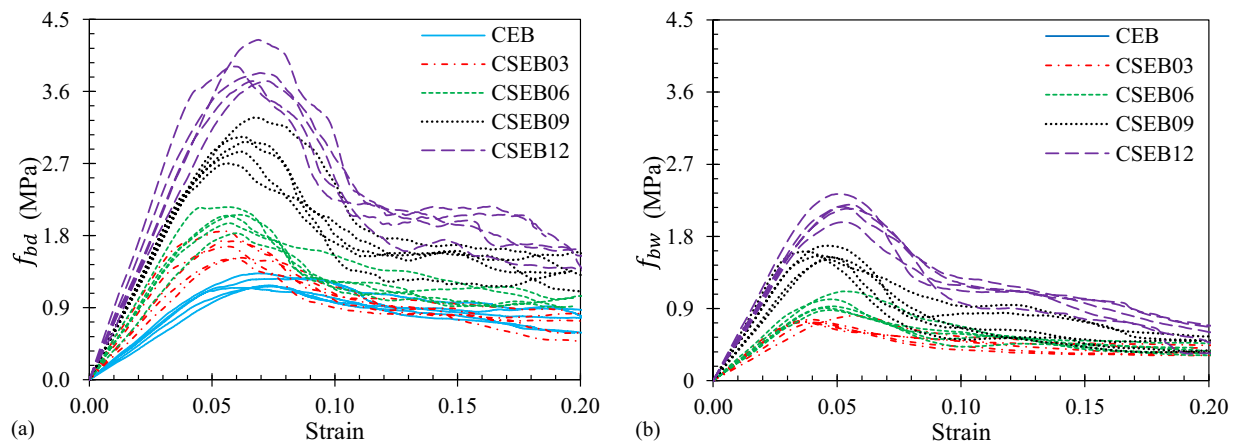**Fig. 7.** Stress-strain curves of CSEBs: (a) dry compression test and (b) wet compression test

observed that soil-sand-cement mortars with 15 wt% cement and 30 or 40 wt% sand had a similar compressive strength to that of CSEB09 and CSEB12 blocks, respectively. Thus, these soil-sand-cement mortars can be used in conjunction with CSEB09 and CSEB12.

### Durability Investigation of CSEB Wall

The performance of a plaster protection for a CSEB masonry wall exposed to the humid weather in Baton Rouge was investigated. A single-wythe 122 cm × 92 cm (4 ft × 3 ft) wall was constructed with CSEBs of 290 mm × 150 mm × 75 mm (11.41 in × 5.90 in × 2.95 in) on June 6, 2015, outside Atkinson Hall, at the LSU School of Architecture in Baton Rouge, LA. Soils B and C were mixed together in equal parts to make soil BC, which was used to produce CSEBs with 6 wt% Type II PC. The particle-size distribution of the reconstituted soil BC is reported in Fig. 3. Five of these earth blocks were tested after 28 days curing to determine their flexural and dry compressive strength, which are reported in Table 3 in terms of sample

means and coefficients of variation. These specimens are identified as CSEB<sup>I</sup> hereinafter to indicate that they were tested before the construction of the wall.

The wall was divided into two parts: a protected side (side P) and an unprotected side (side U). The plaster protection of side P comprised two layers: a 12-mm-thick layer of soil-cement stucco made with soil BC and 6 wt% PC covered by a thin layer of cement paste paint, as shown in Fig. 8. The wall was left exposed to outdoor weather conditions for six months and was visually inspected twice a week to observe and document the condition of the wall. After one-month of the exposure, the initiation of erosion was observed on the surface of the CSEBs on the unprotected side of the wall. This erosion progressed with time on the unprotected side, as shown in Fig. 8(b). After three months, the CSEBs at the top corner of the unprotected side of the wall lost their bond with the wall due to degradation of the blocks and the mortar in the top two courses, as shown in Fig. 8(c). Fig. 8(d) shows the wall on December 10, 2015, before it was carefully dismantled. Two blocks at the top corner of the unprotected side were slightly dislodged, and one of them was

cracked in the middle. By contrast, the protected side of the wall did not show any sign of distress after six months of weather exposure. The blocks from both the protected (CSEB<sup>P</sup>) and unprotected (CSEB<sup>U</sup>) side were recovered and carefully moved to the structural laboratory. Among the recovered blocks that were undamaged under visual inspection, five specimens from each side of the wall were subjected to flexure and compression testing using the same procedure previously described. The results of these experimental tests are reported in Table 3 in terms of sample means and coefficients of variation for the flexural and dry compressive strengths and the corresponding MOE.

The average MOR and dry compressive strength of the CSEB<sup>P</sup> are 72% and 19% higher than those of the CSEB<sup>U</sup>, respectively, which demonstrates the effectiveness of the double layer plaster in protecting the wall from deterioration due to weather action. In addition, the average MOR and dry compressive strength of the CSEB<sup>P</sup> are 11% and 23% higher than those of the CSEB<sup>I</sup>. This phenomenon may be due to the progress of cement hydration under the high humidity conditions experienced by the wall. It is also observed that the average compressive strength of the CSEB<sup>U</sup> is slightly higher than that of the CSEB<sup>I</sup>, whereas the average MOR is significantly lower. This phenomenon may be due to the counteracting effects of cement hydration (which tends to increase the block strength and seems to be dominant for compressive strength) and superficial erosion (which tends to produce imperfections and cracks and seems to be dominant for flexural strength).

The results of this durability investigation confirm that humid weather produces very demanding conditions for CSEBs and that an exterior coating is needed to mitigate erosion and degradation induced by severe weather conditions. The proposed dual layer

plaster consisting of a soil-cement stucco with a coat of cement paste was effective in protecting a CSEB wall from the humid climate that is typical of the U.S. Gulf Coast region. However, further investigation is needed to determine an optimal, cost-effective option for protection of CSEB structures.

### Hurricane Wind Resistance of CSEB Systems

The hurricane wind resistance of CSEB systems built using local soil was investigated by using the parametric strength demand curves developed by Matta et al. (2015) to identify the minimum acceptable wall thickness for the main wind-force resisting system of one-story single-family dwellings made of CSEB masonry and located in exposure zone C (ASCE 2013). These parametric curves for CSEB structures with flat roofs are shown in Fig. 9. The horizontal axis represents the basic wind speed (defined as the 3-s gust speed at 10 m aboveground in exposure zone C), the vertical axis indicates the compressive strength of earth block masonry, and the different curves with markers identify the masonry strength required at any given wind speed for CSEB systems with walls of different thickness. The horizontal dashed lines labeled as M09 and M12 identify the characteristic masonry strength for earth block masonry built with: (1) CSEB09 blocks and soil-sand-cement mortar with 15 wt% cement and 30 wt% sand and (2) CSEB12 blocks soil-sand-cement mortar with 15 wt% cement and 40 wt% sand, respectively. The characteristic compressive strength of the masonry walls was determined as  $f_c = 1.64$  MPa for M09 and  $f_c = 2.14$  MPa for M12, respectively, by using the following equation recommended in Eurocode 6 (CEDN 2005)

$$f_c = 0.55 f_{bd}^{0.7} f_m^{0.3} \quad (1)$$

Where  $f_c$  denotes the characteristic compressive strength of the masonry. This equation was preferred to other expressions available in the literature and in other design codes (Francis et al. 1971; Khoo and Hendry 1973; Hendry 1998; MSJC 2011) because it applies to the strength ranges considered in this study and it is the most conservative relations among those available in the literature (Zucchini and Lourenço 2007). The vertical solid lines identify the design wind speeds (ASCE 2013) for some of the major cities in Louisiana, i.e., Shreveport, Lafayette, Baton Rouge, New Orleans, and Houma.

The results reported in Fig. 9 indicate that: (1) in Shreveport and Lafayette, a wall of thickness  $t = 254$  mm is sufficient for both M09 and M12; (2) in Baton Rouge, a wall of thickness  $t = 305$  mm and 254 mm are needed for M09 and M12, respectively; and (3) in New Orleans and Houma, the minimum wall thickness for M09 and M12 increases to  $t = 356$  mm and 305 mm respectively. Considering the dimension of the blocks, an earth block wall with  $t = 254$  mm can be built using a single-wythe configuration (Guillaud et al. 1995; Auroville Earth Institute 2017), whereas larger wall thicknesses would require a double-wythe configuration. It is noted here that the required wall thickness could be further reduced, e.g., by using

**Table 2.** Dry Compressive Strength and MOE of Mortar Cubes

Cement content (%)	Sand content (%)	$f_m$		MOE		$f_{mk}$ (MPa)
		Avg. (MPa)	COV (%)	Avg. (MPa)	COV (%)	
3	0	0.38	7.47	5.44	17.55	0.23
6	0	0.55	17.89	11.44	27.50	0.25
9	0	0.94	2.19	18.24	45.98	0.63
12	0	1.33	7.28	27.06	15.26	0.79
15	0	1.74	4.89	34.32	14.52	1.10
18	0	1.94	9.43	39.94	18.58	1.10
21	0	2.38	9.06	44.88	24.12	1.36
24	0	2.88	6.87	51.78	24.70	1.74
27	0	3.40	4.10	57.50	23.18	2.18
30	0	3.89	8.39	61.18	13.38	2.26
15	20	2.22	2.17	53.76	30.78	1.49
15	30	3.01	6.92	68.54	10.79	1.81
15	40	3.91	9.21	77.84	15.47	2.23
15	50	4.41	10.83	86.02	20.48	2.41

**Table 3.** Mechanical Properties of CBEBs before Construction and after Demolition of the Wall

Tested specimens	Flexure test				Compression test			
	MOR		MOE		$f_{bd}$		MOE	
	Avg. (MPa)	COV (%)	Avg. (MPa)	COV (%)	Avg. (MPa)	COV (%)	Avg. (MPa)	COV (%)
CSEB <sup>I</sup>	0.57	11.28	164.32	22.00	1.38	6.40	31.22	16.98
CSEB <sup>P</sup>	0.64	22.68	279.51	17.11	1.79	5.55	55.61	20.21
CSEB <sup>U</sup>	0.37	21.82	143.33	31.60	1.50	13.80	44.78	26.82




**Fig. 8.** Durability study of a CSEB masonry wall exposed to Baton Rouge weather: (a) wall after construction; (b) wall after 1 month of exposure; (c) wall after 3 months of exposure; and (d) wall after 6 months of exposure

steel reinforcement (Matta et al. 2015), or a different set of optimized block sizes could be used (Guillaud et al. 1995; Rigassi 1995; Auroville Earth Institute 2017).

### Architectural Feasibility Study

In response to the need for affordable and climate responsive housing in coastal Louisiana, single-family prototype designs were developed using CSEBs as the primary construction element. In appreciation of the rich cultural heritage and environmental context of the U.S. Gulf Coast region, the proposed prototype housing designs embrace many qualities inherent to local vernacular architecture, which includes Creole and Acadian influences and presents a heritage of building types composed of common elements that evolved from living in a hot wet climate (Edwards and Kariouk Pecquet du Bellay de Verton 2004). Fundamental aspects, incorporated into the housing designs, include deep porches, high ceilings, floor-to-ceiling openings, raised ground floors, and program-specific room volumes, which all help to facilitate air movement by means of passive crossventilation.

Two significant housing types, i.e., the shotgun and the dogtrot (Edwards and Kariouk Pecquet du Bellay de Verton 2004), were considered in the design of two single-family prototypes. Each prototype was based on a single-family program of around 1000 square

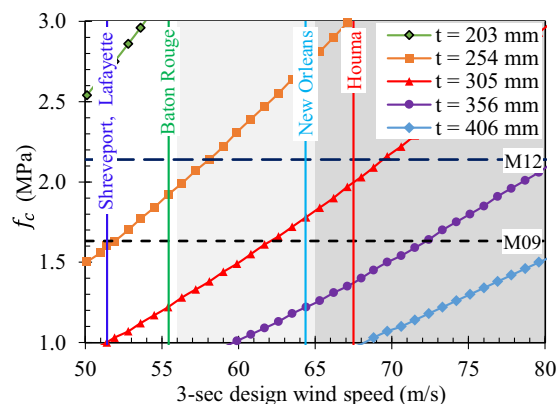

**Fig. 9.** Parametric design curves for main wind-force resisting system of CSEB single-story houses with flat roofs


feet on one level with an interior volume of 10 to 12 ft in height. They are composed of a main living area, kitchen, bathroom, two bedrooms, and outdoor porches. Beyond these equivalent features, unique characteristics of the housing designs were developed based on specific contextual qualities. The shotgun prototype, based on customs of the Creole who migrated from Haiti, is an urban house




and has a long thin linear arrangement of rooms for efficient cross-ventilation and minimal frontage following the organization of dense inner-city land allotment (see Fig. 10). A covered exterior porch faces the street and is open on the sides to promote social interaction with adjacent neighbors. The dogtrot prototype, based on customs of the Acadians who came from Nova Scotia, is a rural house and has an organization based on a central porch (which provides ventilation for adjacent rooms), flanked by public living spaces on one side and private on the other (see Fig. 11). The mass of the dogtrot house has a recessed, inward facing porch that

functions as an entry way and a private social space in less dense rural communities.

The proposed designs were developed around an architectural logic based on the 254 mm × 152 mm × 76 mm (10 in × 6 in × 3 in) module of the CSEB. On top of the foundation, a stem wall (made of a triple layer of earth blocks) with a height of 76.2 cm (2.5 ft) supports an elevated floor to promote improved air circulation and ventilation. For the shotgun prototype, the load-bearing exterior wall continues vertically from the stem wall and is reinforced by a series of transverse walls that function as buttress bracing for lateral loads,

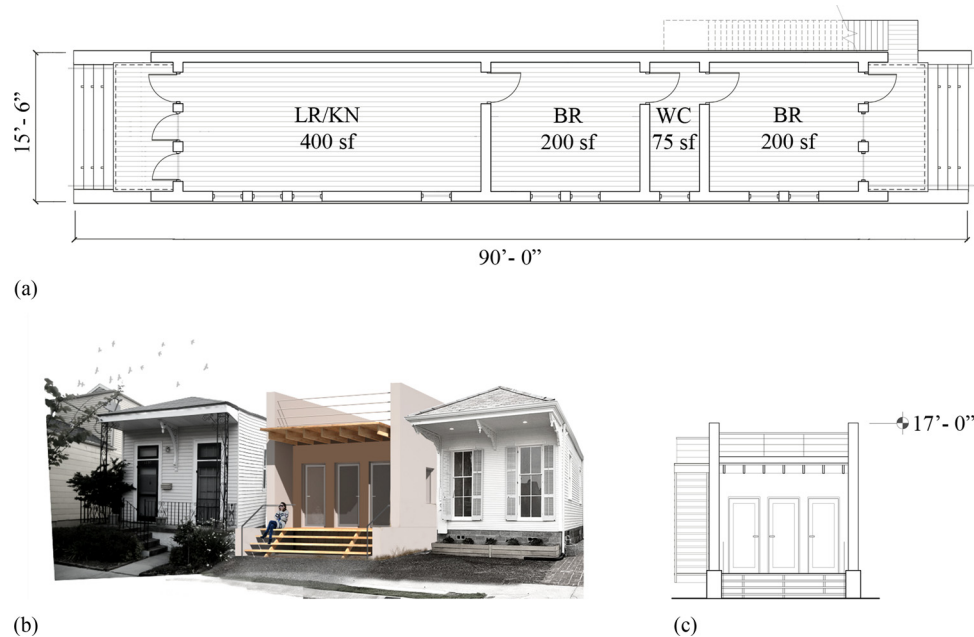

**Fig. 10.** Drawings of the shotgun prototypes house: (a) floor plan, (b) front perspective (rendering), and (c) front elevation (1 ft = 30.48 cm, 1 in. = 2.54 cm, and 1 sq ft = 0.093 m<sup>2</sup>)

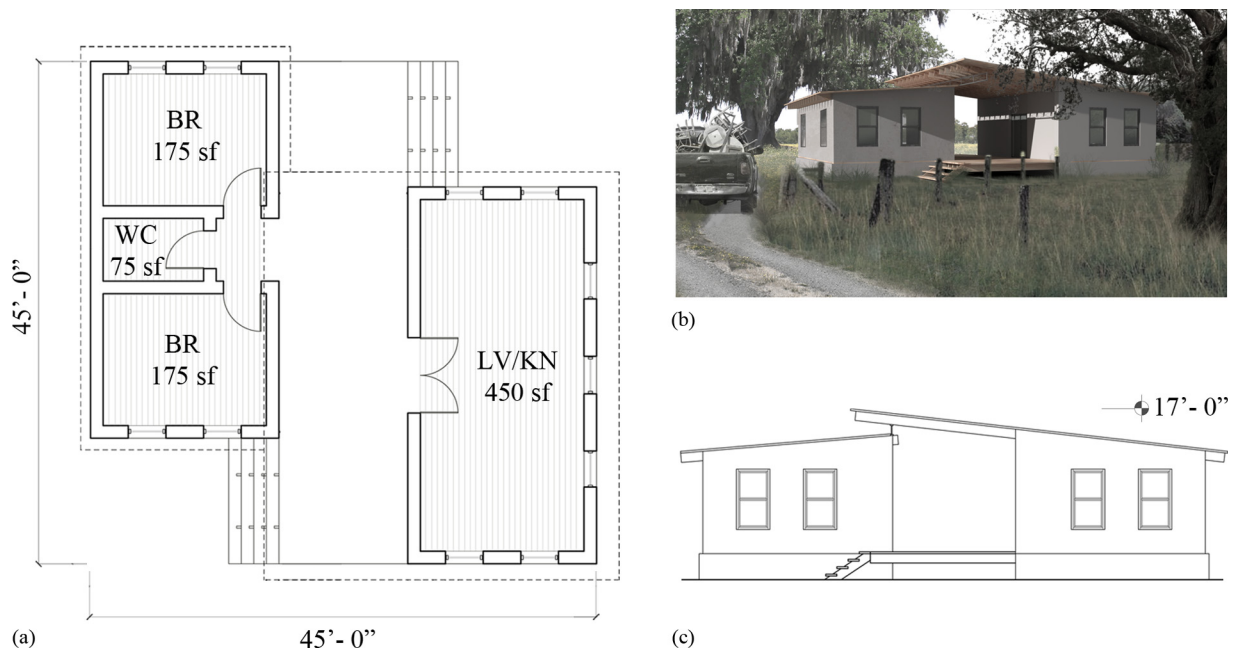


**Fig. 11.** Drawings of the dogtrot prototypes house: (a) floor plan, (b) front perspective (rendering), and (c) front elevation (1 ft = 30.48 cm, 1 in. = 2.54 cm, and 1 sq ft = 0.093 m<sup>2</sup>)

with a maximum span between transverse walls of 9.14 m (30 ft). The exterior wall is finished with the proposed dual layer plaster to provide weather protection. Door and window openings are supported by wood box frames. All components, details, and connections were kept intentionally simple to help achieve the goal of affordable materials and labor that are readily available. An exploded axonometric illustration of the different assemblies for the shotgun prototype house is presented in Fig. 12. Roofs, foundations, and their connections with the walls were dimensioned to resist the wind lateral and uplift forces, which were calculated based on the envelope procedure for enclosed simple diaphragm low-rise buildings given in ASCE 7-10 (ASCE 2013). The roof joists are connected to the walls through steel hurricane ties.

It is concluded that CSEB systems can be adapted to design and build simple houses based on local vernacular architecture. Thus, CSEB houses can have the appearance of houses built using other more traditional construction techniques, which could promote their acceptance among local populations.

## Economic Feasibility Study

An economic feasibility study was performed to determine whether CSEB structures could represent a sustainable approach for affordable, safe, and weather resistant housing in the U.S. Gulf Coast region. Based on the mechanical properties identified in the structural feasibility study, the shotgun prototype with 1000 ft<sup>2</sup> area was considered as a reference single-family dwelling. The cost to build this house was compared to the costs of equivalent houses built using light-frame wood construction, fired brick masonry, and concrete block masonry. For the sake of comparison, components other than the walls (e.g., foundation, roof, and floor systems) were assumed to be equal and, thus, have the same costs for all houses compared here. It is noted here that this assumption is only an approximation and that further study is needed to investigate whether and how much the cost of these other components is affected by the usage of different wall systems. However, this investigation is outside the scope of this paper.

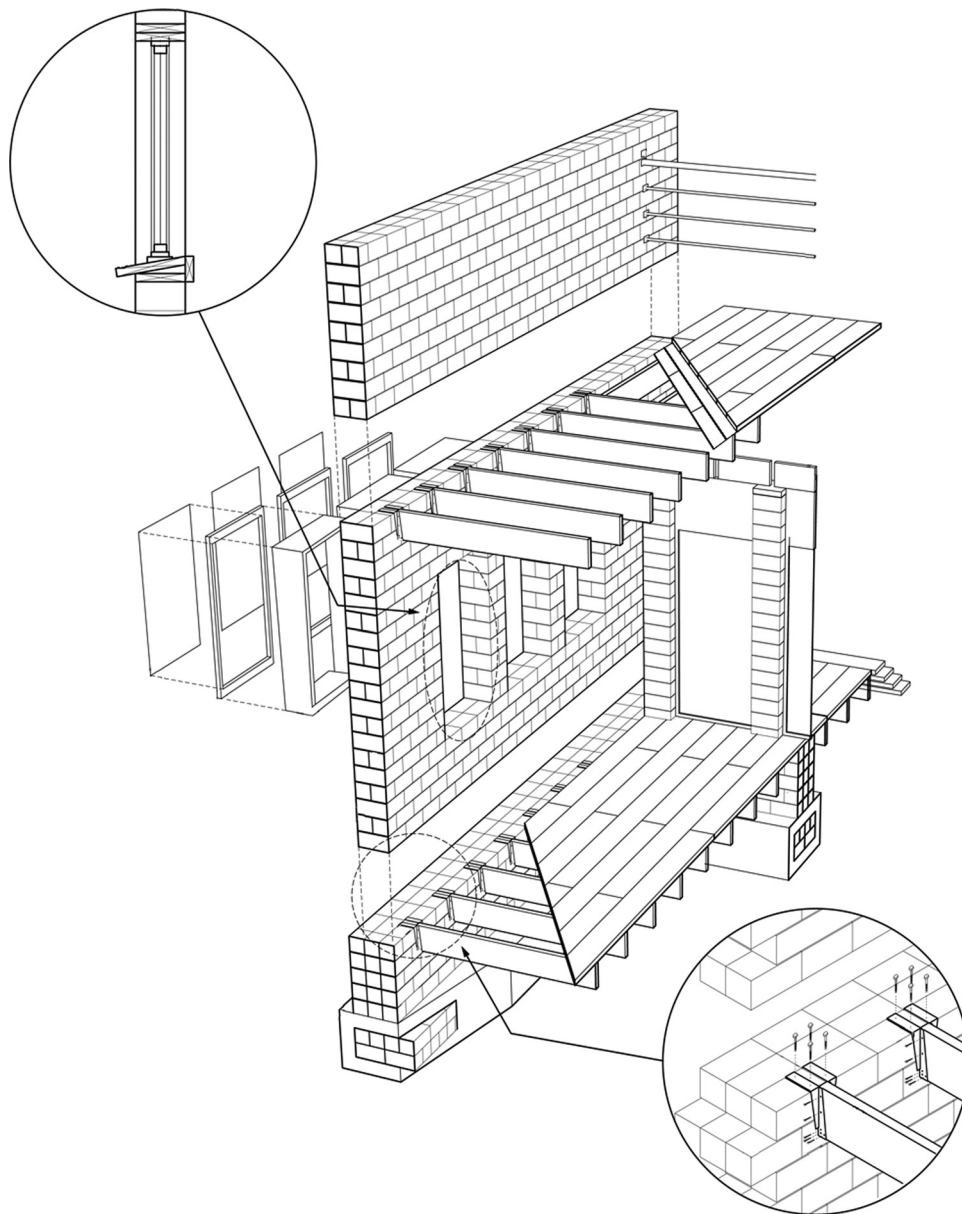

**Fig. 12.** Exploded axonometric illustrations of the different assemblies in the shotgun prototype house

Two construction options were considered for the CSEB walls, namely (1) CSEB walls built using mortar layers of typical thickness to provide the bond between blocks (Guillaud et al. 1995), referred to as mortared CSEB wall hereinafter (Fig. 13) and (2) CSEB walls built with interlocking CSEBs (ICSEBs) with thin layers of mortar slurry and grouted vertical steel reinforcement (Wheeler 2005), referred to as mortarless ICSEB wall (Fig. 13). In the mortarless ICSEB wall option, the reinforcement consisted of #4 steel reinforcing bars at 406.4-mm center-to-center spacing and was used to speed up the construction process. The detailed cost estimates for all components of these two CSEB wall options are reported in Table 4. The total number of blocks needed for construction was estimated at 9680 for the mortared CSEB wall and 10938 for the mortarless ICSEB wall. All costs were determined using the average national costs of material and labor and applying the appropriate city cost index for Baton Rouge, LA (RSMeans Engineering Staff 2015). The labor cost for the CSEB walls included block fabrication, construction, stucco installation (only on exterior walls), and masonry painting. The number of man-hours required for building a unit area of mortared CSEB wall was assumed equal to those required to build ordinary fired clay masonry walls when using skilled labor (RSMeans Engineering Staff 2015). A 50% reduction of labor hours was considered for building mortarless ICSEB wall walls relative to the labor needed for mortared CSEB wall (Dwell Earth 2016). In addition, it was assumed that semi-skilled workers could build mortarless ICSEB walls under the supervision of a skilled mason (Dwell Earth 2016). These two assumptions were based on existing literature on drystack mortarless masonry (Harris et al. 1992, Hines 1993) and on information obtained by conducting a survey among active U.S. earth-block builders (B. De Jong, personal communication).


The costs of light-frame wood, fired brick, and concrete block walls for the same reference prototype house were also determined by considering national average costs adjusted by the city cost index for Baton Rouge, LA (RSMeans Engineering Staff 2014, 2015), as

shown in Table 5. In addition to the costs of materials and labor, the overhead for general contractors and the costs associated with other components of the house (i.e., concrete footing, light-frame wooden floor, light-frame wooden roof, interior ceiling, doors and windows, kitchen, bathroom, and electric system) were estimated and are reported in Table 5. Finally, Table 5 reports the relative costs of the wall systems and entire houses built using the different materials and considering the mortarless ICSEB wall system as reference.

It is observed that, among the solutions considered in this study, the mortarless ICSEB wall system is the least expensive option, with a wall cost ratio (WCR) equal to 1.00, followed by the light-frame wood (WCR = 1.053), concrete block (WCR = 1.208), mortared CSEB (WCR = 1.489), and fired-brick (WCR = 1.723) wall systems. The cost of the mortarless ICSEB system is very similar to that of a light-frame wood wall system, which is the most commonly used construction technique for housing construction in the region (van de Lindt and Dao 2009). On the contrary, the cost of the mortared CSEB wall system is significantly higher than that of wooden frame walls. This result makes the mortared CSEB wall system economically unfeasible, unless the owners of the house are also its builders. It is noteworthy that this circumstance is quite common in rural settings and in developing countries, where this type of construction is often adopted by low-income families that can provide the labor (Houben and Guillaud 1994; Norton 1997).

## Conclusion

This paper presented the results of a feasibility study for CSEB construction in the U.S. Gulf Coast region, which included structural, architectural, and economic components. Based on the results of the structural component of this feasibility study, the following conclusions are drawn: (1) the soil available in the East Baton Rouge area is suitable for fabricating CSEBs; (2) the CSEBs fabricated with at least 9% in weight (wt%) of cement content satisfy the minimum strength requirements for building single-story dwellings; (3) soil-

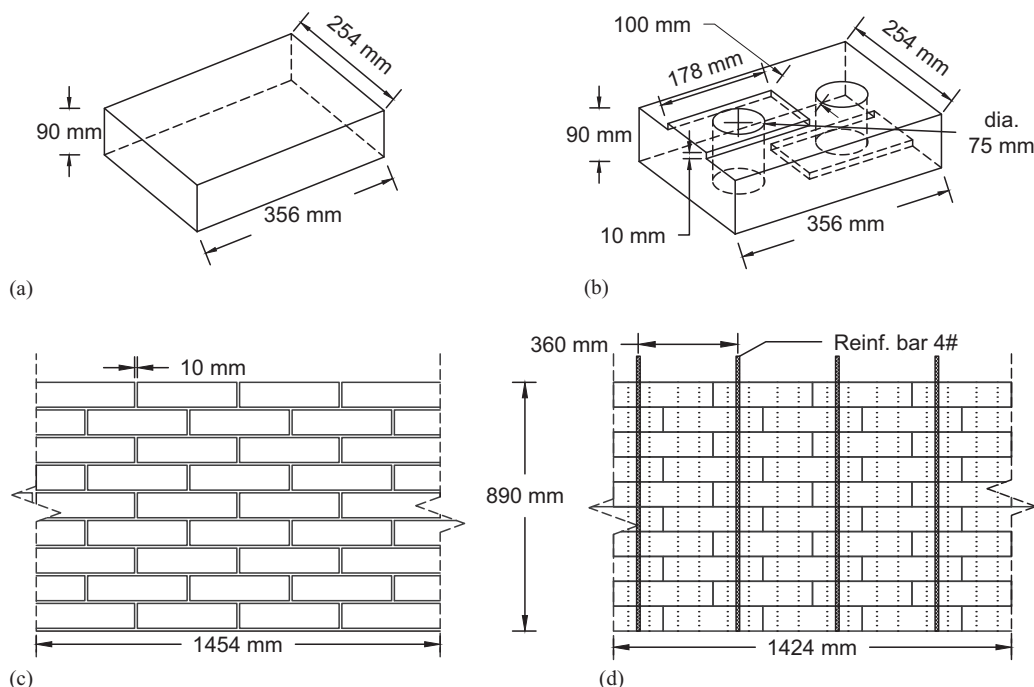

**Fig. 13.** CSEB wall systems: (a) ordinary CSEB element; (b) ICSEB element; (c) mortared CSEB wall system; and (d) mortarless ICSEB wall system

**Table 4.** Detailed Cost Estimates of CSEB Walls for Reference Prototype House

Components	Items	Mortarless ICSEB wall			Mortared CSEB wall		
		Quantity	Unit	Cost (\$)	Quantity	Unit	Cost (\$)
Blocks	Soil	133.3	Ton	—	132.6	Ton	—
	Cement	40,055	lbs.	3,676	39,851	lbs.	3,651
	Labor	584	Hours	4,234	528	Hours	3,828
	Machine	73	Hours	2,555	66	Hours	2,310
Reinforcement	Material	1,610	lbs.	483	—	lbs.	—
	Labor	29	Hour	580	—	Hour	—
Mortar & grout	Soil	10.6	Ton	—	10.6	Ton	—
	Cement	7,806	lbs.	720	7,806	lbs.	720
	Sand	10.6	Ton	531	10.6	Ton	530
Masonry work	Stem walls	113	Hours	2,250	225	Hours	5,721
	Long walls	288	Hours	5,766	577	Hours	14,755
	Short walls	92	Hours	1,830	183	Hours	4,683
Rendering	Soil	2.7	Ton	—	2.7	Ton	—
	Cement	2,938	lbs.	271	2,938	lbs.	271
	Sand	2.7	Ton	133	2.7	Ton	133
	Masonry paint	5,964	ft <sup>2</sup>	1,372	5,964	ft <sup>2</sup>	1,372
	Plastering	87	Hours	2,185	87	Hours	2,185
	Painting	48	Hours	1,193	48	Hours	1,193
	<b>Total cost</b>			<b>27,779</b>			<b>41,352</b>

**Table 5.** Cost Comparison of Different Wall Systems for Reference Prototype House

Items	Mortarless ICSEB	Mortared CSEB	Light-frame wood	Bricks	Concrete blocks
Material (\$)	7,186	6,676	15,638	19,533	12,844
Labor (\$)	20,593	34,674	13,068	27,625	20,255
Overheads (\$)	11,112	16,540	12,264	19,840	13,882
Total wall cost (\$)	38,891	57,890	40,970	66,997	46,981
Total cost of assemblies (\$)	65,110	65,110	65,110	65,110	65,110
Total cost of house (\$)	104,001	123,000	106,080	132,107	112,091
Wall cost ratio (-)	1.000	1.489	1.053	1.723	1.208
House cost ratio (-)	1.000	1.183	1.020	1.270	1.078

sand-cement mortars with 15 wt% cement and at least 30 wt% sand can be used in conjunction with CSEBs; (4) exterior CSEB walls need a protection from the weather conditions in a humid climate, and dual-layer plaster consisting of a soil-cement stucco with a coat of cement paste seems to provide a sufficient protection; and (5) hurricane-resistant earthen dwellings can be built using single- or double-wythe earth block masonry walls. The architectural feasibility investigation indicates that CSEB systems can be adapted to design based on local vernacular architecture, which could promote their acceptance from the local population. Finally, the economic feasibility study suggests that mortarless ICSEB wall can be built at a lower cost than other traditional wall systems, i.e. (in order of increasing average cost), light-frame-wood, concrete-block, and fired-clay-brick wall systems; whereas a mortared CSEB wall system is less expensive than only fired-clay-brick walls, due to the high amount of labor required for their construction.

The feasibility study presented in this paper shows that earthen dwellings built using mortarless ICSEB wall systems can be an attractive choice for low-cost hurricane-resistant housing in the U.S. Gulf Coast region. However, further detailed investigations are required to understand the performance of earthen dwellings and to provide guidance in the design and code development for this

type of structures. In particular, both experimental and numerical investigations are needed to determine the structural resistance and reliability of CSEB systems against extreme loads due to natural hazards (e.g., high winds and earthquakes), the appropriate dimensioning and performance of different type of reinforcements, the effects of different stabilizers and fabrication procedures on the performance of CSEBs and CSEB masonry, as well as the proper configurations of architectural and structural details (e.g., taller foundation walls to separate the wall from the wet soil, alternative wall coating and/or rendering surfaces, shading/shielding elements, specific roofing and grading details, connections between walls and foundation and/or between walls and roof, details of window and door openings).

### Acknowledgments

Partial support for this research by (1) the Louisiana Board of Regents through the Economic Development Assistantship Program, (2) the Louisiana State University's Coastal Sustainability Studio through the 2014-2015 New Projects Fund Program, and (3) the National Science Foundation through award CMMI #1537078 is

gratefully acknowledged. The authors also thank Dr. Fabio Matta of the University of South Carolina (Columbia, SC) for sharing the data on the parametric design curves for CSEB houses. Finally, the authors acknowledge the help received at the beginning of this work from Dr. Ashok Mishra, Mr. Mirsardar Esmaili, Chris Doiron, and James Babin.

## References

- ASCE (2013). "Minimum design loads for buildings and other structures." *ASCE/SEI 7-10*, Reston, VA.
- ASTM (2009). "Standard test methods for particle-size distribution (gradation) of soils using sieve analysis." *D6913-04*, West Conshohocken, PA.
- ASTM (2010a). "Standard practice for classification of soils for engineering purposes (Unified Soil Classification System)." *D2487-11*, West Conshohocken, PA.
- ASTM (2010b). "Standard test method for liquid limit, plastic limit, and plasticity index of soils." *D4318-10*, West Conshohocken, PA.
- ASTM (2016a). "Standard test method for compressive strength of hydraulic cement mortars (using 2-in. or 50-mm cube specimens)." *C109/C109M-16a*, West Conshohocken, PA.
- ASTM (2016b). "Standard test method for particle-size distribution (gradation) of fine-grained soils using the sedimentation (hydrometer) analysis." *D7928-16*, West Conshohocken, PA.
- Auroville Earth Institute. (2017). (<http://www.earth-auroville.com>) (Mar. 31, 2017).
- Avrami, E. C., Guillaud, H., and Hardy, M. (2008). "Terra literature review: An overview of research in earthen architecture conservation." Getty Conservation Institute, Los Angeles.
- Blondet, M., Vargas, J., and Tarque, N. (2008). "Observed behaviour of earthen structures during the Pisco (Perú) earthquake of August 15, 2007." *Proc., 14th World Conf. on Earthquake Engineering*, International Association for Earthquake Engineering, Tokyo.
- Brown, J., Evans, M. and Morrow, C. (2014). *Model block press*. California Polytechnic State Univ., San Luis Obispo, CA.
- CEDN (2005). "Eurocode-6 design of masonry structures-part 1-1: General rules for reinforced and unreinforced masonry structures." *EN 1996-1-1*, Brussels, Belgium.
- Cuéllar-Azcárate, M. C., and Matta, F. (2016). "Recycled-plastic reinforced earthen masonry prototype for tornado-resistant dwellings." *Proc., 16th International Brick and Block Masonry Conf.*, C. Modena, F. da Porto, and M. R. Valluzzi (eds.), Taylor & Francis, Abingdon, U.K., 829–834.
- Davenport, C., and Robertson, C. (2016). "Resettling the first American 'climate refugees'." *The New York Times*.
- Deboucha, S., and Hashim, R. (2011). "A review on bricks and stabilized compressed earth blocks." *Sci. Res. Essay.*, 6(3), 499–506.
- Delgado, M. C. J. and Guerrero, I. C. (2007). "The selection of soils for unstabilised earth building: A normative review." *Construction and Building Materials*, 21(2), 237–251.
- Dwell Earth. (2016). (<http://dwellearth.com>) (Apr. 12, 2017).
- Edwards, J. D., and Kariouk Pecquet du Bellay de Verton, N. (2004). *A creole lexicon: Architecture, landscape, people*, Louisiana State University Press, Baton Rouge, LA.
- Emrath, P. (2014). "Impact of home building and remodeling on the U.S. economy." *Economics and housing policy*, National Association of Home Builders, Washington, DC.
- Francis, A. J., Horman, C., and Jerrems, L. (1971). "The effect of joint thickness and other factors on the compressive strength of brickwork." *Proc., 2nd International Brick Masonry Conf.*, 31–37.
- Gandreau, D. and Delboy, L. (2012). *World heritage inventory of earthen architecture, 2012*. United Nations Educational Scientific and Cultural Organization, Grenoble, France.
- Geiger, O. (2011). "Impact testing earthco megablocks with blackpowder cannon." Natural Building Blog. (<http://www.naturalbuildingblog.com/impact-testing-earthco-megablocks-with-blackpowder-cannon/>) (Sep. 25, 2017).
- Gomes, M. I., Lopes, M. and De Brito, J. (2011). "Seismic resistance of earth construction in Portugal." *Eng. Struct.*, 33(3), 932–941.
- Gooding, D. E. M. (1994). "Improved processes for the production of soil-cement building blocks." Ph.D. dissertation, Univ. of Warwick, Coventry, U.K.
- Guettala, A., Abibsi, A., and Houari, H. (2006). "Durability study of stabilized earth concrete under both laboratory and climatic conditions exposure." *Constr. Build. Mater.*, 20(3), 119–127.
- Guettala, A., Houari, H., Mezghiche, B., and Chebili, R. (2002). "Durability of lime stabilized earth blocks." *Courrier du Savoie*, 2, 61–66.
- Guillaud, H., Joffroy, T., and Odul, P. (1995). *Compressed earth blocks: Manual of design and construction*, Deutsche Gesellschaft für Technische Zusammenarbeit (GTZ) GmbH, Eschborn, Germany.
- Hall, M. R., Lindsay, R., and Krayenhoff, M. (2012). *Modern earth buildings: Materials, engineering, constructions and applications*, Woodhead Publishing Limited, Philadelphia.
- Harris, H., Oh, K., and Hamid, A. (1992). "Development of new interlocking and mortarless block masonry units for efficient building systems." *Proc., the 6th Canadian Masonry Symp.*, Univ. of Saskatchewan, Saskatoon, SK, Canada.
- Hendry, A. W. (1990). *Structural masonry*, Scholium International, London.
- Hines, T. (1993). "Benefits of drystack interlocking concrete masonry as a component of cost effective construction." *Proc., the Sixth North American Masonry Conf.*, The Masonry Society, 849–861.
- Houben, H., and Guillaud, H. (1994). *Earth construction: A comprehensive guide*, Intermediate Technology Publications, London.
- Inter-American Housing Planning Center. (1964). "Soil cement: Its use in building." *Report. No. E.64.IV.6*. United Nations. Department of Economic and Social Affairs, New York, USA.
- Kerali, A. G. (2001). "Durability of compressed and cement-stabilised building blocks." Ph.D. dissertation, Univ. of Warwick, Coventry, U.K.
- Khoo, C.-L. and Hendry, A. (1973). "Failure criterion for brickwork in axial compression." *Proc., 3rd International Brick and Block Masonry Conf.*, 139–145.
- Klingner, R. E. (2006). "Behavior of masonry in the Northridge (U.S.) and Tecoman–Colima (Mexico) earthquakes: Lessons learned, and changes in U.S. design provisions." *Constr. Build. Mater.*, 20(4), 209–219.
- Korkmaz, H. H., Korkmaz, S. Z., and Donduren, M. (2010). "Earthquake hazard and damage on traditional rural structures in Turkey." *Nat. Hazards Earth Syst. Sci.*, 10, 605.
- LHFA (2010). *Louisiana housing needs assessment 2010 executive summary*. GCR & Associates, Inc., New Orleans.
- Lunt, M. G. (1980). "Stabilised soil blocks for building." *Building in hot climates. A selection of overseas building notes*, Her Majesty's Stationery Office, London, 127–144.
- Maillard, P., and Aubert, J. E. (2014). "Effects of the anisotropy of extruded earth bricks on their hygrothermal properties." *Constr. Build. Mater.*, 63, 56–61.
- Matta, F., Cuéllar-Azcárate, M. C., and Garbin, E. (2015). "Earthen masonry dwelling structures for extreme wind loads." *Eng. Struct.*, 83, 163–175.
- Meriani, S. (2008). "Available technologies for local building materials." *International Centre for Science and High Technology*, Trieste, Italy. (<https://institute.unido.org/wp-content/uploads/2014/11/12.-Available-technologies-for-local-building-materials.pdf>) (Mar. 12, 2018).
- Middleton, G. F., and Schneider, L. M. (1992). *Earth-wall construction*, 4th Ed., Commonwealth Scientific and Industrial Research Organization Div. of Building, Construction and Engineering, North Ryde, NSW, Australia.
- Minke, G. (2012). *Building with earth: Design and technology of a sustainable architecture*, Birkhäuser–Publishers for Architecture, Boston.
- Morton, T., Stevenson, F., Taylor, B., and Charlton Smith, N. (2005). "Low cost earth brick construction—2 Kirk Park, Dalguise: Monitoring & evaluation." *Technical Rep.*, Arc Chartered Architects, Fife, U.K.
- NMAC (2009). "Title 14, Chapter 7, Part 4: New Mexico earthen building materials code." The Commission of Public Records Administrative Law Div., Santa Fe, NM.
- Norton, J. (1997). *Building with earth: A handbook*, Intermediate Technology Publications, Rugby, U.K.

- Pacheco-Torgal, F., and Jalali, S. (2011). *Eco-efficient construction and building materials*. Springer, London, UK, ISBN 978-0-85729-892-8.
- Rigassi, V. (1995). *Compressed earth blocks: Manual of production*, Deutsche Gesellschaft für Technische Zusammenarbeit (GTZ) GmbH, Eschborn, Germany.
- Riza, F. V., Rahman, I. A., and Zaidi, A. M. A. (2011). "Preliminary study of compressed stabilized earth brick (CSEB)." *Aust. J. Basic Appl. Sci.*, 5(9), 6–12.
- RSMMeans Engineering Staff. (2014). *RSMMeans residential cost data 2015*, Gordian RSMMeans Data, Rockland, MA.
- RSMMeans Engineering Staff. (2015). *RSMMeans concrete and masonry cost data 2016*, Gordian RSMMeans Data, Rockland, MA.
- Sayın, E., Yön, B., Calayır, Y., and Karaton, M. (2013). "Failures of masonry and adobe buildings during the June 23, 2011 Maden-(Elazığ) earthquake in Turkey." *Eng. Fail. Anal.*, 34, 779–791.
- SNZ (1998). "Engineering design of earth buildings." *SNZ-4297*, Standards New Zealand, Wellington, New Zealand.
- Taylor, M. R. (1988). "Fort Selden test wall status report." *Proc., 5th International Meeting of Experts on the Conservation of Earthen Architecture*, Imprimerie Guirimand, Grenoble, France, 91–102.
- Taylor, M. R. (1990). "An evaluation of the New Mexico State Monuments adobe test walls at Fort Selden." *Proc., 6th International Conf. on the Conservation of Earthen Architecture*, Getty Conservation Institute, Los Angeles, 383–389.
- USDA (1999). *Soil taxonomy: A basic system of soil classification for making and interpreting soil surveys*, 2nd Ed., U.S. Dept. of Agriculture, Natural Resources Conservation Service, Washington, DC.
- van de Lindt, J. W., and Dao, T. N. (2009). "Performance-based wind engineering for wood-frame buildings." *J. Struct. Eng.*, 10.1061/(ASCE)0733-9445(2009)135:2(169), 169–177.
- Venkatarama Reddy, B. V., and Gupta, A. (2005). "Characteristics of cement-soil mortars." *Mater. Struct.*, 38(6), 639–650.
- Venkatarama Reddy, B. V., and Gupta, A. (2006). "Tensile bond strength of soil-cement block masonry couplets using cement-soil mortars." *J. Mater. Civ. Eng.*, 10.1061/(ASCE)0899-1561(2006)18:1(36), 36–45.
- Walker, P. (1996). "Specifications for stabilised pressed earth blocks." *Masonry Int.*, 10(1), 1–6.
- Walker, P. (1999). "Bond characteristics of earth block masonry." *J. Mater. Civ. Eng.*, 10.1061/(ASCE)0899-1561(1999)11:3(249), 249–256.
- Walker, P., and Stace, T. (1997). "Properties of some cement stabilised compressed earth blocks and mortars." *Mater. Struct.*, 30(9), 545–551.
- Webb, D. J. T. (1988). "Stabilised soil building blocks." Ph.D. dissertation, Newcastle Univ., Newcastle Upon Tyne, U.K.
- Weismann, A., and Bryce, K. (2006). *Building with cob*, Green Books, London.
- Wheeler, G. (2005). *Interlocking compressed earth blocks, volume II. Manual of construction*, Center for Vocational Building Technology, Udonthani, Thailand.
- Windstorm, B., and Schmidt, A. (2013). "A report of contemporary rammed earth construction and research in North America." *Sustainability*, 5(12)(2), 400–416.
- Zucchini, A., and Lourenço, P. B. (2007). "Mechanics of masonry in compression: Results from a homogenisation approach." *Comput. Struct.*, 85(3–4), 193–204.